

## International Journal of Bio-Inorganic Hybrid Nanomaterials

### Preparation and Characterization of ZrO<sub>2</sub>/ZnO Nanocomposite under Ultrasonic Irradiation via Sol-gel Route

Shokufeh Aghabeygi<sup>1\*</sup>, Maryam Zare-Dehnavi<sup>2</sup>, Ali Farhadyar<sup>3</sup>, Nazanin Farhadyar<sup>4</sup>

<sup>1</sup> Assistant Professor, Department of Chemistry, East Tehran Branch, Islamic Azad University, Tehran, Iran

<sup>2</sup> Instructor, Department of Chemistry, East Tehran Branch, Islamic Azad University, Tehran, Iran

<sup>3</sup> Ph.D., Agribusiness Department, Armenian State Agrarian University, IRAN

<sup>4</sup> Assistant Professor, Department of Chemistry, Varamin-Pishva Branch, Islamic Azad University, Varamin, Iran

Received: 25 November 2014; Accepted: 28 January 2015

#### ABSTRACT

Nanocomposite of ZrO<sub>2</sub>/ZnO was prepared under ultrasonic irradiation by sol gel process from directly mixing Zirconium and Zinc gels, and the mixture was placed under ultrasonic irradiation for 2 hours then aging time the filtrated composite gel was calcinated at 500°C for 3h in furnace. The precursor sol of zirconium was prepared from an aqueous solution of ZrCl<sub>4</sub> and zinc acetate dihydrated was dissolved in de-ionized water. The FT-IR analysis and the XRD study were exhibited that the crystal structure and purity of the ZrO<sub>2</sub>/ZnO nanocomposite FESEM images was indicated the morphology and the average size of the NPs. The average size of the ZrO<sub>2</sub>/ZnO nanocomposite was determined 37 nm.

**Keyword:** Zirconia ZnO; Nanocomposite; Particle size; Sol-gel; Ultrasonic irradiation.

## 1. INTRODUCTION

In recent years, there has been increasing interest in the application of nano size Zirconia and Zinc oxide for catalysts and supports, ceramics, inorganic membranes, gas sensing, water purification and solar energy conversion [1,2]. ZrO<sub>2</sub> has unique characteristics, such as weak acidity, basicity, redox and high thermal stability. Since the beneficial physical-chemical properties strongly depend on the particle size, the controlled and reliable preparation of nano-ranged materials represents a particular challenge being reflected by numerous ap-

proaches, for instance flame synthesis [3], chemical vapor deposition [4], Sol-gel processes [5], hydrothermal synthesis [6], sonocation [7] and polyol synthesis [8]. Due to its unique properties ZrO<sub>2</sub> is widely used for gas sensors, ceramics, sorbents and catalysts; concerning the latter, ZrO<sub>2</sub> is particularly employed as catalyst carrier in the selective catalytic reduction of NO<sub>x</sub> by NH<sub>3</sub> (SCR) [9-11]. In most cases, the precursors are soluble zirconium salts like ZrO(NO<sub>3</sub>)<sub>2</sub>.xH<sub>2</sub>O, Zr(NO<sub>3</sub>)<sub>4</sub>, ZrO-Cl<sub>2</sub>.xH<sub>2</sub>O and ZrCl<sub>4</sub> [12-15], whereas organic zirconi-

(\*) Corresponding Author - e-mail: saghabeygi@yahoo.com

um compounds have been used as well [16,17].

Moreover, the sol-gel method allows for the homogeneous mixing of transition-metal cations at a molecular level, which enhances the formation of polycrystalline particles with special properties [18]. The crystalline phase of  $ZrO_2$  strongly influences its catalytic activity and selectivity [19, 20].

More attention has been paid to ZnO nanostructures because ZnO is an important low cost basic II–VI wide band gap semiconductor material which is used considerably for its catalytic, electrical, photoelectrical and photodegradation properties [21]. Recently using of ultrasonic irradiation has been employed of synthesis and sono-catalyst properties of many nano materials [21, 22].

We have been synthesized the binary nanocomposite of  $ZrO_2/ZnO$  by using ultrasonic irradiation, the ultrasonic probe is very effective in preparation process.

## 2. EXPERIMENTAL

### 2.1. Preparation of Zinc gel

4.4 g (0.2 mol)  $Zn(CH_3COO)_2 \cdot 2H_2O$  was firstly dissolved in DI water (100 mL) and stirred to get a precursor solution. 15 mL (2M)  $NH_4OH$  solution was then dropped into the precursor solution until pH of mixture was adjusted 9 and the white suspension of  $Zn(OH)_2$  was appeared. After that, the mixture was continuously stirred for 2 days then the tip of ultrasonic probe was introduced into the mixture and it was irradiation under ultrasonic irradiation for 30 min to




achieve a ZnO homogenous gel.

### 2.2. Preparation of Zirconium gel

Firstly  $ZrCl_4$  (4.7g, 0.2 mL) was dissolved in 2-propanol (100 mL) to get a precursor solution. A solution of  $H_2O_2$  (6 mL, 30% v/v) was then dropped into the precursor solution under stirring. The pH of mixture was adjusted 9 by adding ammonium solution 2M until Zirconium gel ( $Zr(OH)_4$ ) was prepared and the produced gel was aged and stirring for 2 days, Then the probe of ultrasonic was introduced in  $ZrO_2$  gel and it was irradiated for 30 min.

### 2.3. Preparation of $ZrO_2/ZnO$ nanocomposite

The Zirconium and Zinc gels were mixed together then the mixture gels were irradiated by the probe of ultrasonic instrument for 2 h. The mixture was stirred for 48 h, then it was filtrated and washed several times. After drying at room temperature, the white precipitated was calcinated at  $500^\circ C$  for 3 h in furnace.



## 3. RESULTS AND DISCUSSION

### 3.1. FESEM image

Surface and morphology of the synthesized nanocomposite have been studied and the FESEM images are

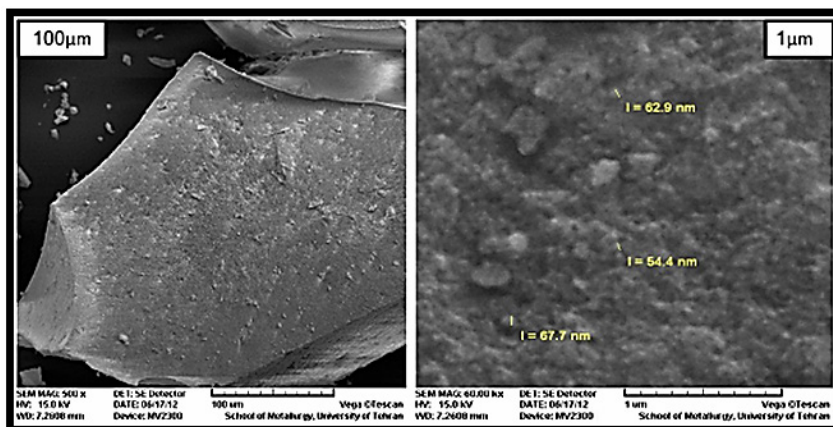


Figure 1: FESEM images of  $ZrO_2/ZnO$  nanocomposite.

shown in Figure 1. The  $ZrO_2/ZnO$  nanoparticles are seen uniform. The size of particles is 50-60 nm

### 3.2. XRD diffraction

The XRD pattern of the  $ZrO_2/ZnO$  nanocomposite is shown in Figure 2. The distinct peaks corresponding to ZnO and  $ZrO_2$  are observed. It is concluded that both the materials exist in perfect crystalline phases and retain their physical structure and hence confirmed to form a  $ZrO_2/ZnO$  nanocomposite (according to card no. 37-1484 for  $ZrO_2$  and card no. 36-1451, for ZnO Joint Committee on Powder Diffraction Standards (JCPDS)). The  $ZrO_2/ZnO$  nanoparticles are seen pure. The average particle size  $D_v$  of crystallites in the composite was also roughly calculated based upon the XRD spectra for quantitative purpose using the Scherrer equation:

$$D_v = \frac{K\lambda}{\beta \cos \theta}$$

where:  $D_v$  is the “volume weighted” crystallite size =  $\frac{3}{4} d$  (crystallite diameter)  $K$  is the “Scherrer constant” (around 0.9),  $\lambda$  is the wavelength of the X-Rays here is  $\lambda$ ,  $CuK\alpha = 1.541 \text{ \AA}$ ,  $\theta$  is the Bragg angle for the peak at  $2\theta$ ,  $\beta$  is the “integral breadth” of the peak at  $2\theta$ . The  $\beta = (\pi/2)$  FWHM (full width at half maximum) for a Gaussian shaped peak. The crystallite size of  $ZrO_2/ZnO$  nanocomposite according to XRD Pattern is estimated to be 37 nm.

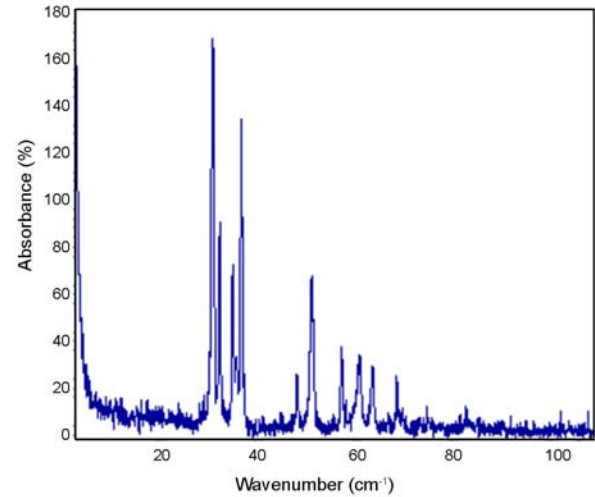


Figure 2: XRD patterns of the  $ZrO_2/ZnO$  nanocomposite powder.

### 3.3. FT-IR analysis

FT-IR spectrum of the  $ZrO_2/ZnO$  nanocomposite is shown in Figure 3, in the wave number range from 4000 to 400  $cm^{-1}$ . The peaks at 567, 671 and 762  $cm^{-1}$  can be attributed to symmetric and asymmetry stretching vibration of the  $Zr-O-Zr$  bond and  $O-Zr-O$  flexion. The peaks at 869  $cm^{-1}$  were attributed to the vibration mode of  $Zn-O-Zr$ . The peaks at 420 and 497  $cm^{-1}$  can be assigned to stretching vibration of the  $Zn-O-Zn$  bond and  $O-Zn-O$  bond respectively. The peak at 1630  $cm^{-1}$  resulted from bending vibration of the adsorbed  $H_2O$  molecules, which were not removed completely after Sol-gel synthesis. The wide peak at

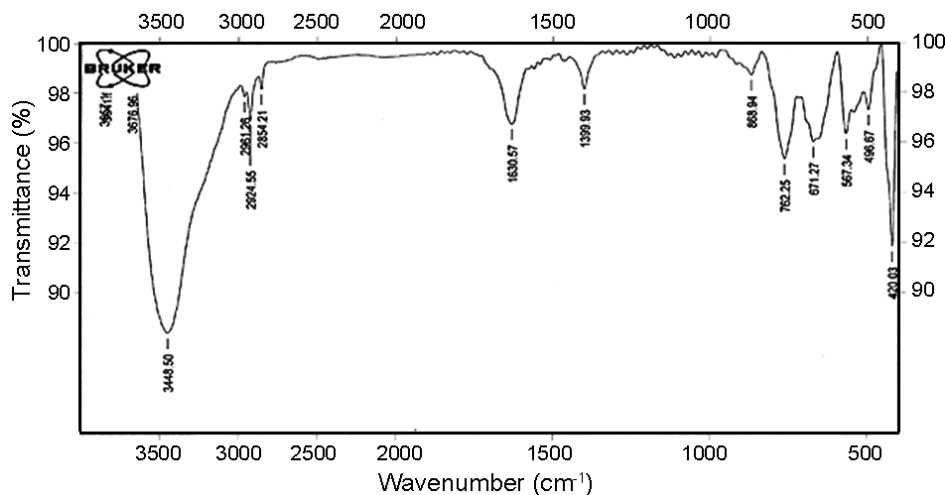


Figure 3: FT-IR spectra of the  $ZrO_2/ZnO$  nanocomposite powder.

3448  $\text{cm}^{-1}$  has been assigned to the OH symmetry and asymmetry stretching vibration of surface hydroxyl group.

#### 4. CONCLUSIONS

ZrO<sub>2</sub>/ZnO nanocomposite has been synthesized by a facile Sol-gel method using ultrasonic irradiation. Zn(CH<sub>3</sub>COO)<sub>2</sub>·2H<sub>2</sub>O and ZrCl<sub>4</sub> have been used as starting materials. The nanocomposite of ZrO<sub>2</sub>/ZnO molar ratio 1:1 was calcinated at 500°C, Comparison of the FT-IR spectra of ZrO<sub>2</sub>/ZnO nanocomposite with the pure ZrO<sub>2</sub> and ZnO nanoparticles have been showed formation of ZrO<sub>2</sub>/ZnO nanocomposite. Crystal phase and particle size of NPs can be detected by XRD. According to XRD Patterns, the calculated value as crystallite size of ZrO<sub>2</sub>/ZnO nanocomposite was obtained around 37 nm.

#### ACKNOWLEDGEMENT

The authors thank the research and technology section of Islamic Azad University East Tehran Branch.

#### REFERENCES

1. Tian J., Chen L., Yin Y., Wang X., Dai J., Zhu Z., Liu X., Wu P., *Surf. Coat. Tech.*, **204** (2009), 205.
2. Djerad S., Geiger B., Schott F.J.P., Kureti S., *Catal. Commun.*, **10** (2009), 1103.
3. Heine M.C., Madler L., Jossen R., Pratsinis S.E., *Combust. Flame*, **144** (2006), 809.
4. Liu Y., Zhu W., Tan O.K., Shen Y., *Mater. Sci. Eng. B*, **47** (1997), 171.
5. Sugimoto T., Sakade K., *J. Colloid Interface Sci.*, **152** (1992), 587.
6. Chhabra V., Ayyub P., Chattopadhyay S., Maitra A.N., *Mater. Lett.*, **26** (1996) 21.
7. Sahu D., Panda N.R., Acharya B.S., Panda A.K., *Ceram. Int.*, **40**, (2014), 11041.
8. Jungk H.O., Feldmann C., *J. Mater. Res.*, **15** (2000), 2244.
9. Apostolescu N., Geiger B., Hizbullah K., Jan M.T., Kureti S., Reichert D., Schott F., Weisweiler W., *Appl. Catal. B*, **62** (2006), 104.
10. Li Y., Cheng H., Li D., Qin Y., Xie Y., Wang S., *Chem. Comm.*, **12** (2008), 1470.
11. Lee B.T., Han J.K., Saito F., *Mater. Lett.*, **59** (2005), 355.
12. Shukla S., Seal S., Vij R., Bandyopadhyay S., *J. Nanopart. Res.*, **4** (2002), 553.
13. Jia Y., Hotta Y., Duran C., Sato K., Watari K., *J. Cera. Soc. Japan*, **113** (2005),380.
14. Dell Agli G., Mascolo G., *J. Eur. Ceram. Soc.*, **20** (2000), 139.
15. Dell Agli G., Colantuono A., Mascolo G., *Solid State Ionics*, **123** (1999), 87.
16. Zhao J., Fan W., Wu D., Sun Y., *J. Mater. Res.*, **15** (2000), 402.
17. Inoue M., Kominami H., Inui T., *Res. Chem. Intermed.*, **24** (1998), 571.
18. Hernandez A., Maya L., Sanchez E.M., *J. Sol-Gel Sci. Technol.*, **42** (2007), 71.
19. Rhodes M.D., Bell A.T., *J. Catal.*, **233** (2005), 198.
20. Li W., Huang H., Li H., Zhang W., Liu H., *Langmuir*, **24** (2008), 8358.
21. Huang M.H., Mao S., Feick H., Yan H.Q., Wu Y.Y., Kind H., Weber E., Russo R., Yang P.D., *Science*, **292** (2001), 1897.