

Bredigite (BG) as a novel nanobioceramic powder; investigation and characterization

H. Gheisari Dehsheikh^{1,*} and E. Karamian²

¹ Department of Mechanical and Industrial, Lenjan Branch, Islamic Azad University, Isfahan, Iran

² Department of Mechanical Engineering, Khomeinishahr Branch, Islamic Azad University, Khomeinishahr, Isfahan, Iran

Received: 14 October 2017; Accepted: 16 December 2017

ABSTRACT: In this project, Bredigite (BG) has been successfully prepared by a modified sol-gel method. Optimization in calcination temperature and mechanical ball milling resulted in a pure and nano-sized powder which characterized by means of X-ray diffraction; scanning electron microscopy, transmission electron microscopy and Fourier transform infrared Spectroscopy. We hypothesized that nano-sized Bredigite (BG) would mimic more efficiently the nanocrystal structure and function of natural bone apatite, owing to the higher surface area, compare to conventional micron-size Bredigite (BG). Accordingly, we used the unique advantage of nanotechnology to improve novel nanobredigite (NBG) particles as a potential candidate for bone tissue regeneration whether as a peri-implant filling powder or in combination with other biomaterials as a composite scaffold.

Keywords: Bredigite (BG); Nano bioceramic powder; SEM; TEM; X-ray diffraction

INTRODUCTION

The science of Nanotechnology has a great potential to improve ultimate biomaterials used for tissue engineering. Engineering systems for controlled release of biological nanomolecules and supplementing scaffolds with inorganic nanoparticles improve tissue function by means of mimicking the natural external cell matrix (ECM). Many attempts in the field of engineering novel nanobiomaterials played a key role in the recapitulation of the basic building blocks of native microenvironment of the cells for replacing tissue deficiencies like bone losses from trauma or diseases (Flischer, *et al.*, 2012). Upon this, the approach of incorporating inorganic nanoparticle into the matrix will progress rapidly.

Although various inorganic nanomaterials have been used to replace damaged bones (Ghasemi-Kahrizsangi, *et al.*, 2017) but silicate biomaterials such as bioglass, CaSiO₃ and Ca-Si-M (M = Mg, Zn, Ti, Zr) ceramics have a significant characteristic of the ability to release Si ions at a concentration that stimulates osteoblast growth and differentiation suggesting their application for bone tissue regeneration (Gheisari dehsheikh, *et al.*, 2015). The superiority of these ceramics in bone tissue regeneration compare to hydroxyapatite and other ceramic scaffolds have been reported and among them Bredigite (BG) with the chemical formula of (Ca₇Mg-SiO₄)₄ both in powder or bulk form possesses slower degradation rate and efficiently has the ability of in-

(*) Corresponding Author-e-mail: Hassan.gh.d@gmail.com

vitro apatite formation and *in vivo* bone regeneration (Ghasemi-Kahrizsangi, *et al.*, 2016). Bredigite (BG) powders and dense ceramics have been shown to be bioactive material for bone regenerations in biomaterial science. Wu and Chung proved the quite better cell growth on (BG) disks compare to the other members of $\text{CaOSiO}_2\text{-MgO}$ systems like hardystonite and akermanite as a result of the reduction in their degradation rates (Ghasemi-Kahrizsangi, *et al.*, 2016). Moreover, this ceramic is higher in mechanical properties when it is synthesized in a dense bulk format. Excellent mechanical stability, high bioactivity properties and appropriate cell biocompatibility features due to slow degradation rate made the (BG) ceramic a hot point of concern among biomaterialists.

In addition, various powder preparation methods have been reported such as solid state reaction, sol-gel, coprecipitation and spray pyrolysis technique (Gheisari dehsheikh, *et al.*, 2017). Among them sol-gel technique was chosen to obtain pure and homogeneous (BG) with no extraneous phase. However, to the best of our knowledge, in none of the previous studies that focused on (BG) powder or bulk scaffolds preparation, investigation and characterization, interests has been taken to the preparation of this exceptionally advantageous bioceramic in nano-size powder format. Keeping the above points in view, this study was aimed to report the chemical synthesis and characterization of the sol-gel prepared bone-like powder of (BG) in a nanostructure type. When we consider replacing bone deficiencies with a synthetic material, it is necessary to mimic natural bone nanostructure as much as possible. In this research, we have focused on developing a substitute for biological apatite in a submicron level considering the advantage of high surface area owing to the nanostructure dimensions.

EXPERIMENTAL

MATERIAL AND METHODS

Magnesium nitrate, Calcium nitrate, TEOS and all other solvent and chemicals were analytical grade from Sigma Chemical (Tc. Litch, MO, USA). A zirconia mechanical ball mill (Taha science, Ben, Germany) has been used to ensure the smallest particle

sizes of the ceramic powder. The morphology of (BG) nanoparticles was examined by Scanning Electron Microscopy (SEM, Hitachi JSM-6700, Tokyo, Japan). The nanopowders were mounted onto sample studs and coated with gold using a sputter-coater (Eiko IF3, Tokyo, Japan) for 4min. The microscope was operated at 15 kV to visualize the sample. The phase composition and structure of prepared samples were examined by X-ray powder diffraction (XRD). A Philips X'PERTMPD X-ray diffractometer (XRD) with Cu $\text{K}\alpha$ radiation at a scan rate of $0.002^\circ/\text{min}$ was used for the crystallographic structural analysis of the sample.

Transmission electron microscopy (TEM, JEOL JSM-7400F field emission transmission electron microscope) was used to determine the particle size of sol-gel prepared (BG) powders. Sample preparation has been done by obtaining a suspension from ultrasonification of the powder in ethanol on a foil surface followed by dropping on a copper grid and finally dried to capture the images by means of TEM. A ZAIES FT-IR-540 + spectrometer were used to record IR spectra using KBr Pellets. FT-IR spectra of the catalysts were recorded by FT-IR spectrophotometer in the range of $200\text{--}1800\text{ cm}^{-1}$ with a resolution of 6 cm^{-1} by mixing the sample with KBr.

Preparation of bredigite nanopowder

The (BG) ceramic was prepared via a modified sol-gel method. Briefly we dissolved the same molar ratio of $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$ and $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ in an absolute ethanol and stirred vigorously for 25 minutes in 85°C to dissolve these precursors in the solvent. $\text{Si}(\text{OC}_2\text{H}_5)_4$ (TEOS) was added to the homogeneous solution and slowly stirred to transform to a wet gel. Drying in an oven at 125°C for 12 hours resulted in a dried powder which was grounded in a hand-mortar, then calcinated at 700°C for 3 h and 1000°C for further 26 hours. Finally it was ball-milled in a zirconia mechanical ball mill for 7 hours to supply bredigite nanopowder.

RESULTS AND DISCUSSION

Preparing micron size (BG) by means of sol-gel method has been previously reported (Boroujerdnia, *et al.*, 2016) but here some modifications in the post-treat-

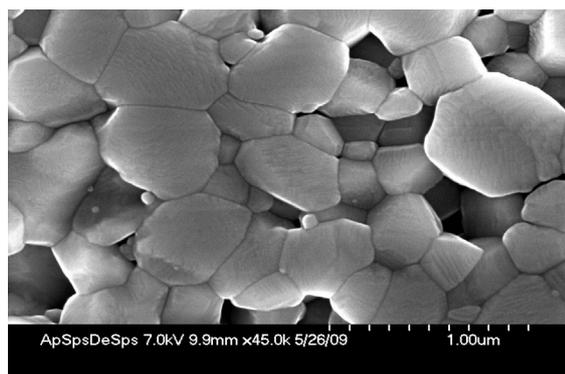


Fig.1. SEM micrograph of bredigite nanopowder.

ments of the as-prepared ceramic including thermal treatments and mechanical manipulations resulted in a pure bredigite nanopowder with particle sizes in the range of 33-55 nm. The (BG) grain size and surface morphology of the particles are shown in Fig.1, indicating that particles agglomerated as a result of high surface energy. However, it is obvious that the dimensions of agglomerated grains are in nano range.

Fig. 2 shows the XRD patterns of the bredigite nanopowder prepared via the sol-gel method and calcinated at different temperatures. Calcination at 700°C resulted in no characteristic peak (Fig. 2). Critical calcination temperature of 1000 °C was obviously ideal to obtain pure (BG) with no impurity of other ceramics. It yielded strong (BG) peaks at about 121°, 120°, 312°, 311°, 131°, which indicates that the dominant resultant of the process is (BG) (Fig. 3). However, in the sample calcinated at temperatures below 1000°C, akermanite, and in higher temperatures, hardys-

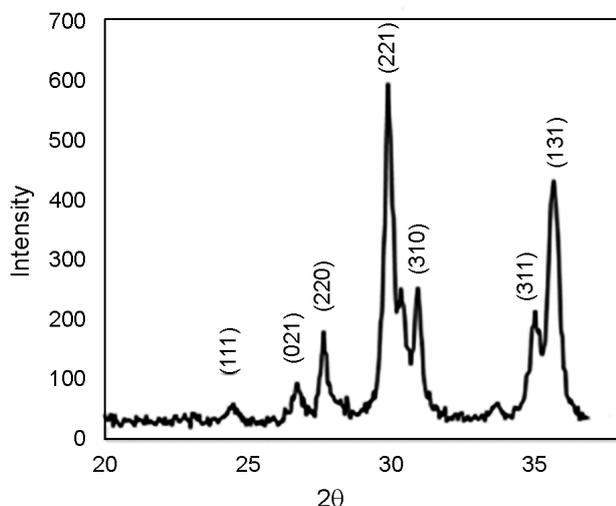


Fig. 2. Pattern of bredigite powders calcinated at different temperatures of 700 °C (A) and 1000 °C (B)

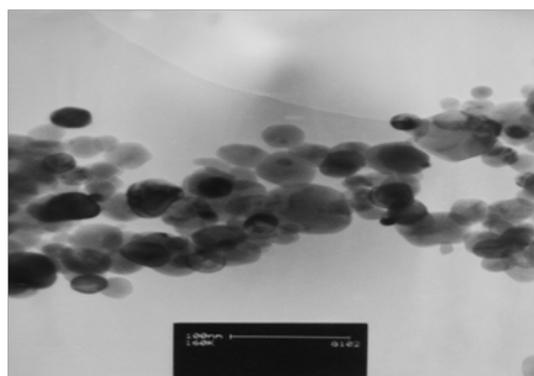


Fig. 3. TEM micrograph of bredigite nanoparticles

tonite was detectable. Furthermore, it is possible to estimate the crystallite size (x_s) in a direction perpendicular to the crystallographic plane of XRD reflection (Gheisari dehsheikh, *et al.*, 2017). Sharper and isolated diffraction peaks such as $2\theta = 56.655^\circ$ were chosen for calculation of the crystallite size. Based on the modified Sherrer formula ($L = K\lambda/\beta\cos\theta$), FWHM is the full width at half maximum for the chosen diffraction peaks in rad (in this case FWHM is equal to 0.002663) and λ is the wavelength of X-ray beam for Cu K α radiation ($\lambda = 1.542$ nm). Accordingly, the average crystallite size of 39.173 was calculated. None of the other chosen peaks for estimation of crystallite size exceeded the result of 38 nm.

Fig. 3 presents the TEM micrograph of the 1000°C heat-treated (BG) and taken images enable the detailed observation of the morphological properties of particles. It shows the spherical border of a non-agglomerated monodisperse particle and particle size of 55 nm.

In the FT-IR spectra of the (BG) bands (Fig. 4) in the 400–2000 cm^{-1} spectral range in the region 750 cm^{-1} can be attributed to the bending vibrations, and bands

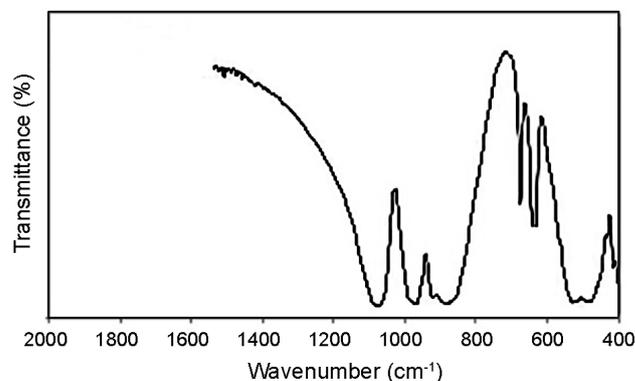


Fig. 4. FT-IR spectra of the bredigite nanoparticles.

in the region 700–1000 cm^{-1} which are attributed to the stretching vibrations of the silicate structure. They ascribed to the Si–O symmetric stretching of bridging & non-bridging oxygen atoms, Si–O–Si symmetric stretching, and Si–O–Si asymmetric stretching. Our results are in agreement with previous studies (Ghasemi-Kahrizangi, *et al.*, 2017).

CONCLUSIONS

Pure (BG) powders were successfully obtained via a simple sol-gel method followed by calcination at 1000 °C. Mechanical grinding in a ceramic ball mill for 6 hours resulted in (BG) nanoparticles in the range of about 33-55 nm. Conventional micron-size (BG) had been previously investigated by many researchers but it is obviously different from bone mineral in the aspect of mimicking the mineral resorption process. Bone crystals of hydroxyapatite are in nano-size dimensions and possess very large surface area. In contrast micron-size particles with lower surface area lack the potency of homogeneous absorption by osteoclasts and miss the unique advantage of nanotechnology for bioactivity and resorbability. Our study suggests that nanobredigite (NBG) might be a potential candidate by itself as a nanobioceramic filling powder or in combination with other biomaterials as a composite scaffold in bone tissue regeneration.

ACKNOWLEDGMENT

The authors are grateful for the kind supports by the Lenjan and Khominishahr Branchs, Islamic Azad University, Isfahan, Iran.

REFERENCES

Ghasemi-Kahrizangi, S., Karamian, E., Gheisari Dehsheikh, H., Ghasemi-Kahrizangi, A. (2017). A Review on Recent Advances on Magnesia-Doloma Refractories by Nano-Technology. *J. Water Environ. Nanotechnol.*, 2(3): 206-222.
Kahrizangi, S. Gh., Nemati, A., Shahraki A., Fa-

rooghi, M. (2016). The effect of nano-additives on the hydration resistance of materials synthesized from the MgO-CaO system. *Int. J. Eng.*, 29: 539-545.

Ghasemi-Kahrizangi, S., Gheisari Dehsheikh, H., Karamian, E., Nemati, A. (2018). A comparative evaluation of the addition impact of nanometer-sized tetravalent oxides on the performance of Doloma-Magnesia ceramic refractories. *Ceram. Int.*, 44(2): 2058-2064.

Boroujerdnia M., Ghasemi-kahrizangi, S., Gheisari-dehsheikh, H. (2016). The effect of nano meter size ZrO_2 particles addition on the densification and hydration resistance of magnesite-dolomite refractories, *Iranian J. Mater. Sci. Eng.*, 13(4): 33-40.

Ghasemi-Kahrizangi, S., Gheisari Dehsheikh, H., Boroujerdnia, M. (2017). MgO-CaO-Cr₂O₃ composition as a novel refractory brick: Use of Cr₂O₃ nanoparticles, *Bol. Soc. Esp. Ceram.* V, 56(2): 83-89.

Ghasemi-Kahrizangi, S., Karamian, E., Gheisari Dehsheikh, H. (2017). The impact of ZrSiO₄ nanoparticles addition on the microstructure and properties of dolomite based refractories. *Ceram. Int.*, 43(16): 13932-13937.

Ghasemi-Kahrizangi, S., Gheisari Dehsheikh, H., Karamian, E., Boroujerdnia, M., Payandeh, Kh. (2017). Effect of MgAl₂O₄ nanoparticles addition on the densification and properties of MgO-CaO refractories. *Ceram. Int.*, 43(6): 5014-5019.

Gheisari Dehsheikh, H., Ghasemi-Kahrizangi, S. (2017). The influence of silica nanoparticles addition on the physical, mechanical, thermo-mechanical as well as microstructure of Mag-Dol refractory composites. *Ceram. Int.*, 43(18): 16780-16786.

Gheisari Dehsheikh, H., Ghasemi-Kahrizangi, S., Karamian, E. (2018). Addition impact of nano-carbon black on the performance of MgO-CaO compounds. *Ceram. Int.*, 44(1): 5524-5527.

Gheisari, H., Karamian E., Abdollahi, M. (2015). A novel hydroxyapatite-hardystonite nanocomposite ceramic. *Ceram. Int.*, 41: 5967–5975.

Gheisari H. and Karamian, E. (2015). Preparation and characterization of hydroxyapatite reinforced with hardystonite as a novel bio-nanocomposite for tis-

sue engineering. *Nanomed. J.*, 2(1): 141-152.
Gheisari Dehsheikh H. and Karamian, E. (2016). Char-

acterization and synthesis of Hardystonite (HT) as
novel bioceramic, *Nanomed. J.*, 3(2): 143-146.

AUTHOR (S) BIOSKETCHES

Hassan Gheisari Dehsheikh, Ph.D., Assistant Professor, Department of Mechanical and Industrial, Lenjan Branch, Islamic Azad University, Isfahan, Iran, *Email: Hassan.gh.d@gmail.com*

Ebrahim Karamian, Ph.D., Assistant Professor, Department of Mechanical Engineering, Khomeinishahr Branch, Islamic Azad University, Khomeinishahr, Isfahan, Iran, *Email: Ebkaramin91@gmail.com*